



ARL-TN-1302 • APR 2026



Evaluation of Aerotron AV as a Maintenance Cleaner Prior to Fluorescent Penetrant Inspection (FPI)

by Scott Grendahl

DISTRIBUTION STATEMENT A. Approved for public release: distribution unlimited.

NOTICES

Disclaimers

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer needed. Do not return it to the originator.



Evaluation of Aerotron AV as a Maintenance Cleaner Prior to Fluorescent Penetrant Inspection (FPI)

Scott Grendahl

DEVCOM Army Research Laboratory

REPORT DOCUMENTATION PAGE

1. REPORT DATE	2. REPORT TYPE	3. DATES COVERED	
April 2026	Technical Note	START DATE 2 September 2024	END DATE 31 March 2026
4. TITLE AND SUBTITLE Evaluation of Aerotron AV as a Maintenance Cleaner Prior to Fluorescent Penetrant Inspection (FPI)			
5a. CONTRACT NUMBER		5b. GRANT NUMBER	5c. PROGRAM ELEMENT NUMBER
5d. PROJECT NUMBER ARL TSA 24-005		5e. TASK NUMBER	5f. WORK UNIT NUMBER
6. AUTHOR(S) Scott Grendahl			
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) DEVCOM Army Research Laboratory ATTN: FCDD-RLA-MF Aberdeen Proving Ground, MD 21005			8. PERFORMING ORGANIZATION REPORT NUMBER ARL-TN-1302
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) AMCOM-G4		10. SPONSOR/MONITOR'S ACRONYM(S)	11. SPONSOR/MONITOR'S REPORT NUMBER(S)
12. DISTRIBUTION/AVAILABILITY STATEMENT DISTRIBUTION STATEMENT A. Approved for public release: distribution unlimited.			
13. SUPPLEMENTARY NOTES			
14. ABSTRACT The U.S. Army Aviation and Missile Command's Environmental Division (G-4) requested that ARL's Biology, Materials, and Manufacturing Sciences Division evaluate Aerotron AV as a maintenance cleaning solvent for use prior to fluorescent penetrant inspection. The results demonstrated that the test product outperformed the standard comparative, methyl ethyl ketone (MEK). Aerotron AV should now be reviewed by the final approval authority for use in the maintenance and overhaul processes at Army depots and airfields.			
15. SUBJECT TERMS fluorescent penetrant inspection, FPI, solvent cleaning, maintenance chemical, crack indications, methyl ethyl ketone, MEK			
16. SECURITY CLASSIFICATION OF:		17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES
a. REPORT UNCLASSIFIED	b. ABSTRACT UNCLASSIFIED	c. THIS PAGE UNCLASSIFIED	UU 14
19a. NAME OF RESPONSIBLE PERSON Scott Grendahl			19b. PHONE NUMBER (Include area code) (520) 691-6051

STANDARD FORM 298 (REV. 5/2020)

Prescribed by ANSI Std. Z39.18

Contents

List of Figures	iv
List of Tables	iv
1. Objective	1
2. Materials and Methods	1
2.1 Test Solutions	1
2.2 Test Specimens	1
2.3 Equipment	1
2.4 Procedure	2
3. Results	3
4. Discussion and Conclusion	5
5. References	6
List of Symbols, Abbreviations, and Acronyms	7
Distribution List	8

List of Figures

Figure 1. Schematic of test cleaning apparatus.	2
Figure 2. MEK Aerotron AV representative indications on R91.....	4
Figure 3. MEK Aerotron AV representative indications on R70.....	4
Figure 4. MEK Aerotron AV representative indications on T62.	5

List of Tables

Table 1. Measured brightness data.....	3
Table 2. Scaled effectiveness.	4

1. Objective

The objective of the testing was to evaluate the effectiveness of Aerotron AV as a vapor degreasing cleaner prior to Fluorescent Penetrant Inspection (FPI), as requested by the U.S. Army Aviation and Missile Command's (AMCOM's) Environmental Division (G-4). This evaluation was conducted under the guidelines of MIL-PRF-32684, Section 3.9.5.¹ Methyl ethyl ketone (MEK) was used as a control cleaning agent for comparison.

2. Materials and Methods

2.1 Test Solutions

- MEK (standard control cleaner)
- Aerotron AV

2.2 Test Specimens

Three fatigue precracked test bars were used:

- R70: Inconel 718 (precrack ~0.090-inch L × 0.020-inch D × 0.001-inch W)
- R91: Inconel 718 (precrack ~0.020-inch L × 0.005-inch D × 0.001-inch W)
- T62: Ti 6-4 (precrack ~0.060-inch L × 0.017-inch D × 0.0005-inch W)

2.3 Equipment

- UV Measurement:
 - Photo Research Photomultiplier-Tube Optical Photometer Model UBD PR-1500 Spectra Spotmeter
 - Spectroline Model SB-100 Super High Intensity UV Lamp (10K+ $\mu\text{W}/\text{cm}^2$)
 - Spectroline Model DSE-100X Photometer with Spectroline Model DIX-365 UV-A sensor
- Cleaning Apparatus: a refluxing apparatus for vapor degreasing simulation, as depicted in Figure 1.

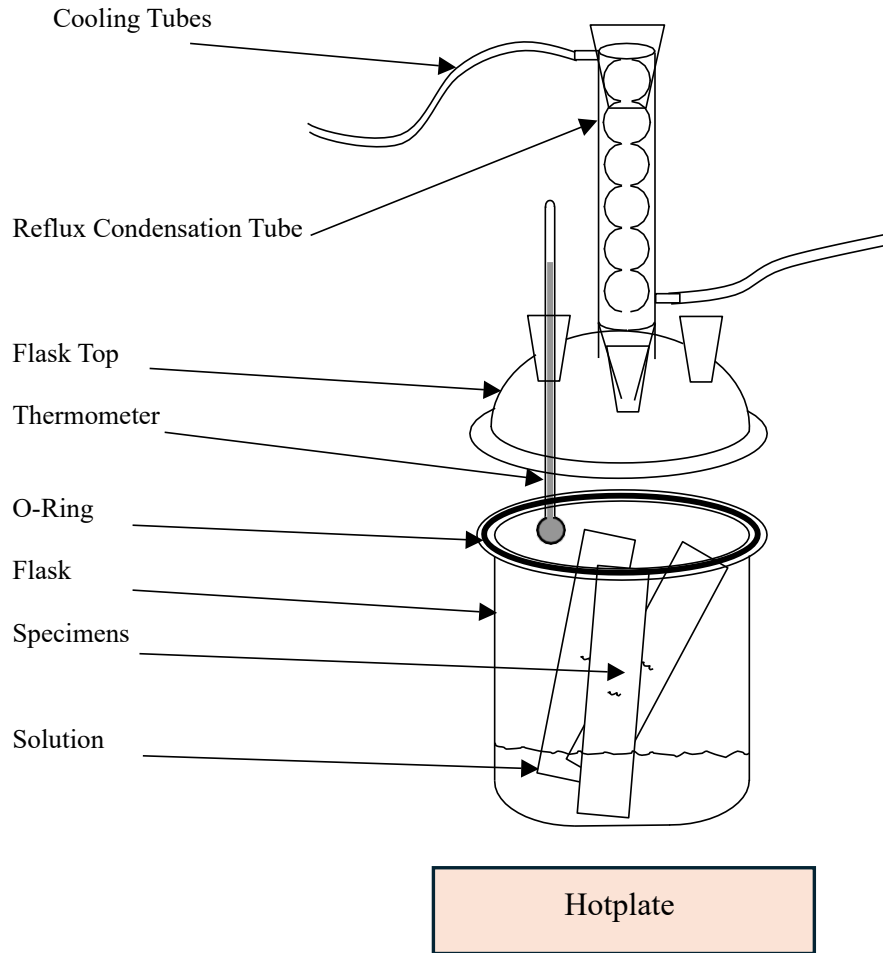


Figure 1. Schematic of test cleaning apparatus.

2.4 Procedure

The test cleaning procedure simulated vapor degreasing using a 10-min cleaning cycle. The steps were as follows:

- 1) Pre-clean with MEK solvent control cleaner.
- 2) Apply a standard contaminant mixture (hydraulic fluid, MoS₂ grease, carbon black) to the crack area and bake at 130 °F.
- 3) Wipe off excess contaminant with a clean towel.
- 4) Perform solvent cleaning in the test fluid for one 10-min cycle.
- 5) Cool the specimen to room temperature.
- 6) Apply Type I, Method C, Sensitivity Level 4 penetrant to the crack area with a dwell time of 5 min.
- 7) Wipe off excess penetrant with a dry, lint-free cloth.
- 8) Perform a solvent wipe with a lint-free cloth.
- 9) Apply Form A, Dry Powder developer with a dwell time of 5 min.

- 10) Perform quantitative brightness measurement with a light meter, using a standardized angle of incidence, standoff, and UV light intensity ($10K+ \mu W/cm^2$).
- 11) Postclean with a deionized (DI) water rinse.
- 12) Postclean with an aqueous cleaner followed by a hot DI rinse.
- 13) Postclean with the MEK vapor degreasing simulator for a 10-min cycle.
- 14) Repeat steps 1–13 for each test fluid and specimen across three test runs with each test specimen.

3. Results

The brightness of the fluorescent indications was measured quantitatively with the apparatus listed. The collected data are summarized in Tables 1 and 2. Representative photographs are depicted below for comparison with each test specimen in Figures 2, 3, and 4, respectively, for specimens R91, R70, and T62.

Table 1. Measured brightness data.

Solvent cleaner	Specimen no.	Test run no.	Spot meter reading	Background reading	Total brightness of indication
MEK	R 91	1	66.7	0.03	66.67
	R 70	1	378	0.04	377.96
	T 62	1	84.3	0.02	84.28
Aerotron AV	R 91	1	63.1	0.01	63.09
	R 70	1	363	0.03	362.97
	T 62	1	71.0	0.02	70.98
MEK	R 91	2	64.9	0.03	64.87
	R 70	2	365	0.01	364.99
	T 62	2	78.8	0.03	78.77
Aerotron AV	R 91	2	72.4	0.03	72.37
	R 70	2	389	0.02	388.98
	T 62	2	86.7	0.01	86.69
MEK	R 91	3	58.5	0.01	58.49
	R 70	3	361	0.03	360.97
	T 62	3	90.1	0.02	90.08
Aerotron AV	R 91	3	61.8	0.03	61.77
	R 70	3	371	0.01	370.99
	T 62	3	68.9	0.02	68.88

Table 2. Scaled effectiveness.

Specimen no.	Average brightness (three measurements)	Scaled effectiveness (MEK = 100%)
MEK with R91	63.37	100
MEK with R70	368	100
MEK with T62	84.4	100
Aerotron AV with R91	65.77	103.8
Aerotron AV with R70	374.33	101.7
Aerotron AV with T62	78.87	93.4

R91 with MEK R91 with Aerotron AV

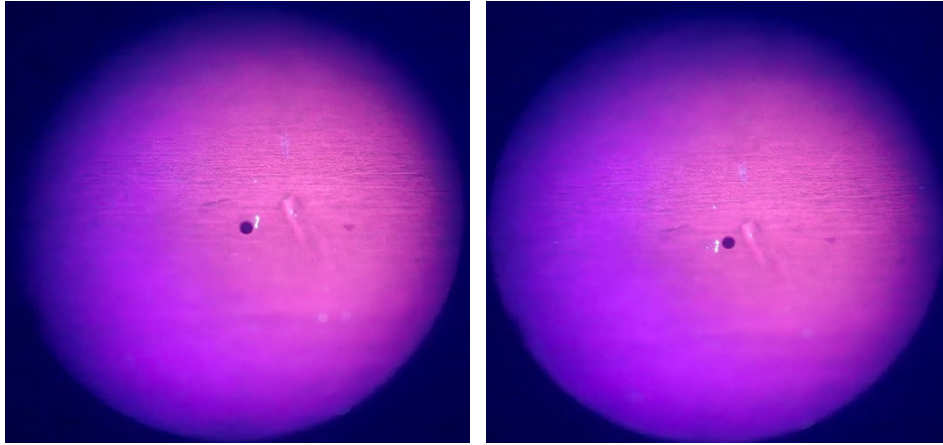


Figure 2. MEK Aerotron AV representative indications on R91.

R70 with MEK R70 Aerotron AV

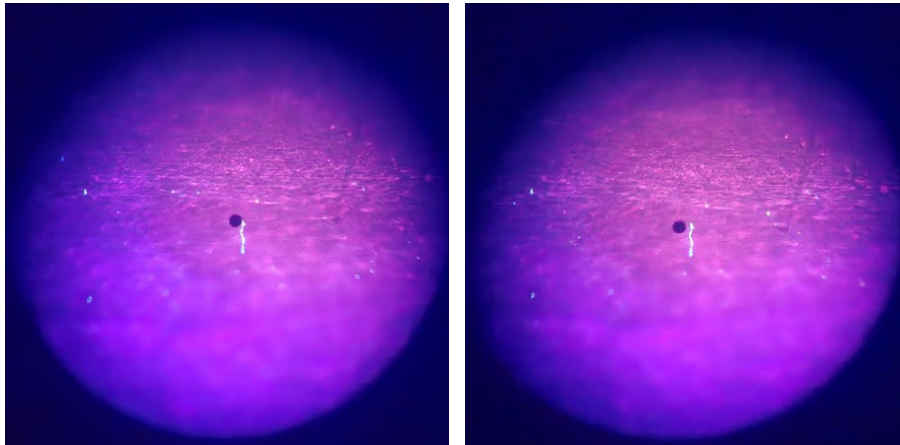


Figure 3. MEK Aerotron AV representative indications on R70.

T62 with MEK T62 with Aerotron AV

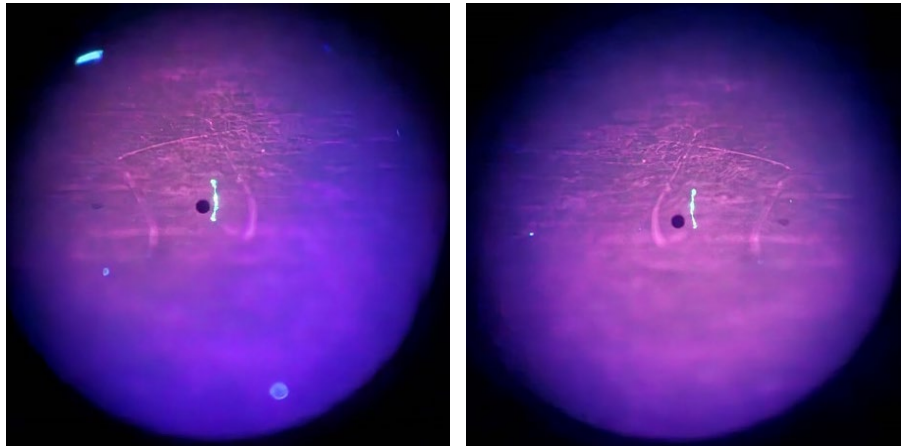


Figure 4. MEK Aerotron AV representative indications on T62.

4. Discussion and Conclusion

The photometer provides a quantitative number to the UV brightness under the black dot in the representative photos while in “spot mode.” Note that these indications (cracks) in the photos are only 20 mil long and this equipment was not designed for photography, as the depth of field (i.e., the focal plane of the lens) is very small. In comparison with the MEK, Aerotron AV appears to be on average, approximately 99% as effective as MEK as a pre-FPI cleaning solvent. The U.S. Army Combat Capabilities Development Command Army Research Laboratory BMMD has observed similar trends in the past with alternative solvents. For some individual tests, MEK outperformed the candidate solvent; however, the alternative was equally effective for the most part. In the past, n-propyl bromide (nPB) alternative solvent was deemed acceptable for vapor degreasing prior to FPI inspection by AMCOM. The comparative study was similar and the results for nPB were lower in comparison with MEK and the test solvent candidates used in this evaluation. Furthermore, nPB proved 85% as effective as MEK, while here the solvent was equally as effective. This was a small-scale study; however, the solvent could be expected to perform as well as the current cleaning solvents in the overhaul and maintenance cycles. The background is much less bright (a good thing) than that observed when using aqueous cleaners and the total brightness was higher in magnitude than that yielded with aqueous cleaners in previous studies. This is subjective, as they were not directly compared here. It can be seen in the representative photos that low background reading is conducive to good contrast between the indication (a crack) and the intact base material that surrounds it.

5. References

1. MIL-PRF-32684. Vapor degreasing solvent. Army (US); 2022 Aug 26.

List of Symbols, Abbreviations, and Acronyms

AMCOM	U.S. Army Aviation and Missile Command
DI	Deionized
FPI	Fluorescent Penetrant Inspection
MEK	Methyl Ethyl Ketone
nPB	n-Propyl Bromide
UV	Ultraviolet

1 DEFENSE TECHNICAL
(PDF) INFORMATION CTR
DTIC OCA

1 DEVCOM ARL
(PDF) FCDD RLB CB
TECH LIB